

Efficient Route for the Synthesis of 1,3-Dioxolanes Catalyzed by Sulfated Mixed Oxides of Yttria-Zirconia

Sandeep S. Kahandal*

Department of Chemistry, V.P.M's B. N. Bandodkar College of Science,
(Autonomous) Thane (W), (Affiliated to University of Mumbai),
Thane, Maharashtra, India

Abstract:- A mild, simple, environmentally benign catalytic protocol for transforming epoxides (oxiranes) into their respective 1,3-dioxolanes. The different epoxides with ketones give exclusively 1,3-dioxolanes catalyzed by sulfated yttria-zirconia with moderate to good yields (A [3+2] cycloaddition approach). The GC and GC-MS analysis shown in most instances that the product obtained was exclusively 1,3-dioxolanes. The catalysts were characterized by using X-ray powder diffraction (XRD), EDAX, FTIR, Thermal methods, and n-butylamine potentiometric titration method. Simple work-up, mild process conditions, and solvent-free approach make the procedure superior to current techniques.

Keywords:- Sulfated yttria-zirconia, 1,3-Dioxolanes, Solvent-free, green chemistry, heterogenous catalysis

I. INTRODUCTION

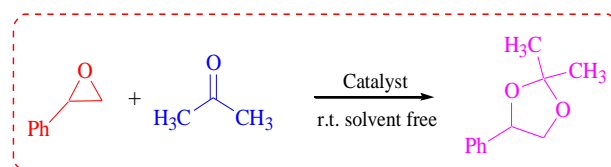
Dioxolane compounds are essential intermediates in various organic processes [1-3]. Alternatively, certain compounds containing 1,3-dioxolane units have physiological and biological properties [4-7]. In the case of aldehydes and ketones in carbohydrates and steroid chemistry, the form of 1,3-Dioxolane is often used as a moiety that protects a carbonyl group. Besides this, diols converted to dioxolanes are used in various spectroscopic and chromatographic techniques [8].

Most often, dioxolanes (acetonides) were synthesized from the reaction of epoxides with compounds containing carbonyl moiety [9]. This transformation was investigated by using $\text{BF}_3 \cdot \text{OEt}_2$ [10], Zeolite [11], HBF_4 , [12], graphene oxide [13], $[\text{Cp}^* \text{Ir}(\text{NCMe})_3]^{2+}$ [14], $\text{MoO}_3/\text{SiO}_2$ [15], $\text{Cu}(\text{OTf})_2$ [16], Chromium-pillared montmorillonite [17], Phosphomolybdic Acid [18], Iron oxide-pillared clay [19], Amberlyst-15 [20], heteropolyacids [21] and 2-methyl benzimidazole-zeolite complexes with d-block metal ions [22]. Boron trifluoride-etherate system was successfully used in the synthesis of 1,3-dioxolanes from carbonyl compounds with only epoxyethane and 2-Methyloxirane [10]. Besides, 1,3-dioxolanes can be synthesized from diols with carbonyl compound using an acid catalyst and azeotropic water extraction conditions. The process is restricted to the carbonyl compounds for both thermal and chemical stability to water under reflux conditions. However, several other catalytic protocols developed more easily and conveniently by converting epoxides to

dioxolanes [23]. The substitution of "non-green" protocols with "green" protocols has industrial relevance to overcome environmental problems. Hence, a viable catalytic protocol that can address these drawbacks must be formulated.

The surface-modified systems of metal and mixed metal oxides are extensively used as solid acid catalysts for various functional group transformations. Sulfated yttria-zirconia used as an efficient catalyst for the pericyclic reaction between a conjugated diene and the dienophile [24], synthesis of β -amino carbonyl compounds [25], protecting hydroxy, thiol and amino groups with carboxylic acids [26], synthesis *N*-Boc protected amines [27] and alkoxycarbonylation of amines [28]. I herein report, the synthesis of 1,3-dioxolanes using a modified form of the yttria-zirconia system as a recyclable catalyst under neat conditions.

To strengthen an environmentally sustainable framework for different organic transformations [29-33], and the outcome obtained for ring opening of oxiranes with nucleophiles [34] encourage exploring surface-modified yttria-zirconia system for acetalization of ketones using oxiranes (Scheme 1). Recyclability of catalysts, neat reaction medium, mild reaction procedure, and environmentally friendly approach make the method more appealing and environmentally sustainable.



Scheme 1: Synthesis of 1,3-dioxolanes from epoxide with carbonyl compounds.

II. MATERIALS AND METHODS

A. Catalyst preparation

Sulfated yttria-zirconia catalysts with varying quantities of yttria loading (4–24 mol.%), were synthesized using coprecipitation followed by the impregnation method [24, 34].

B. A typical procedure for the synthesis of dioxolanes

To a mixture of 2-phenyloxirane (240 mg) and 2-propanone (116 mg), catalyst (24 mg, 10 (wt%) w.r.t. 2-phenyloxirane) was added in 10 mL round bottom flask. For the appropriate time and temperature, the reaction mass has been stirred. During workup, the catalyst was retrieved via

filtration by adding ethyl acetate (5 mL) as a solvent and concentrated to dryness. The progress of the reaction was investigated by using TLC and GC (Thermofisher GC-1000 equipped with a capillary column (30 m × 0.32 mm ID-0.25 μm BP-10) with an FID detector and high purity nitrogen as the carrier gas.) All the products obtained and discussed in this work have been previously reported in the literature and selected compounds characterized by using of Gas chromatography-Mass spectroscopy (Shimadzu QP-2010, E.I. mode with high purity helium as carrier gas).

2,2-Dimethyl-4-phenyl-1,3-dioxolane (Table 2, entry 1); GC-MS (Electron Impact, 70 eV), m/z (%) = 178 (1 %) [M+], 163 (35 %), 148 (5 %), 133 (2 %), 120 (25 %), 103 (8 %), 91 (19 %), 77 (9 %), 72 (65 %), 65 (8 %), 52 (7 %), 48 (100 %).

2-Phenyl-1,4-dioxaspiro[4.5] decane (Table 2, entry 4); GC-MS (Electron Impact, 70 eV), m/z (%) = 218 (70 %) [M+], 189 (25%), 175 (100 %), 162 (10 %), 120 (30 %), 104 (100 %), 91 (50 %).

III. RESULTS AND DISCUSSION

Initially, we studied, the influence of various catalysts for the synthesis of 1,3-dioxolanes at an ambient temperature (Table 1). The reaction conducted without catalysts does not proceed even after a protracted 5 h reaction time for the model reaction of phenyloxirane with 2-propanone (Table 1, entry 1). The reaction of epoxides with ketones was further investigated in the presence of a catalytic amount (10 wt. %) of different catalysts and their surface-modified counterparts. No product was observed with ZrO₂ alone, whereas mixed metal oxide of (Y_{0.16}Zr_{0.84}O₂) gave 30 % yield and sulfated zirconia provided only 34% yield of the 1,3-dioxolanes (Table 1, entries 2-4). In the present investigation, the amount of yttrium present in the catalysts shows a significant effect on the catalytic activity. The acidity values increase from (1.23 to 4.19 mmol. g⁻¹), which reveals good agreement with catalytic activities for a model reaction (Table 1, entries 5-10). The highest catalytic activity observed for SO₄²⁻/Y_{0.16}Zr_{0.84}O₂ (Table 1, entry 8) was due to the highest total acid sites and the initial electrode potential (*E_i*). The measurement of total acid sites and strength was carried out using the potentiometric titration method [35].

Table 1: Study of catalytic activity for the conversion of epoxides to acetones^a

Entry	Catalyst	Acidity (mmol/g) ^b	<i>E_i</i> (mV) ^c	Yield(%) ^d
1 ^e	-	-	-	-
2 ^e	ZrO ₂	0.80	55	-
3	Y _{0.16} Zr _{0.84} O ₂	0.90	91	30
4	SO ₄ ²⁻ /ZrO ₂	2.07	168	34
5	SO ₄ ²⁻ /Y _{0.04} Zr _{0.96} O ₂	1.23	148	47
6	SO ₄ ²⁻ /Y _{0.08} Zr _{0.92} O ₂	1.64	195	55
7	SO ₄ ²⁻ /Y _{0.12} Zr _{0.88} O ₂	1.93	310	78
8	SO ₄ ²⁻ /Y _{0.16} Zr _{0.84} O ₂	4.19	530	95
9	SO ₄ ²⁻ /Y _{0.20} Zr _{0.80} O ₂	2.91	330	67
10	SO ₄ ²⁻ /Y _{0.24} Zr _{0.76} O ₂	2.65	248	50

^aReaction conditions: phenyloxirane (2 mmol), 2-propanone (2 mmol), solvent free, catalyst (24 mg, 10 wt%), solvent free, 2.0 h, Reaction temperature- r.t (32°C), ^bpotentiometric titration method, ^c*E_i*- Initial electrode potential (mV), ^dIsolated yield, ^eReaction time- 5 h.

To generalize the methodology, it was initially established for the reaction of 2-phenyloxirane with various substrates, such as 2-propanone, 1-phenylethanone, 2-butanone, and cyclohexanone, provided 1a-4a products with 84-95% yields (Table 2, entries 1-4).

Sterically hindered 7-oxabicyclo (4.1.0) heptane was found to react sluggishly with 2-propanone and cyclohexanone were provide comparatively lower yields of 5a-6a (Table 2, entries 5-6). Similarly, the reaction of 2-(chloromethyl) oxirane with various ketones also smoothly took place with good yields of 7a-9a (Table 2, entries 7-9). The reaction between 1,2-epoxy-3-phenoxypropane with 2-propanone also smoothly took place provided 88% yield of 10a (Table 2, entry

10). We have also noted that the substituents attached to epoxide and ketones produce a negligible influence on the yield of the products (Table 2, entries 1-10).

The reusability of the catalysts is a crucial aspect that decides the applicability of the catalysts system for industries. We have also executed the recyclability study of catalysts for the reaction of phenyloxirane (20 mmol) with 2-propanone (20 mmol). The catalyst was washed with propanone after separation from the reaction mass and dried for 3 h. in an oven at elevated 120 °C temperature before the succeeding catalytic run. Under experimental conditions, sulfated yttria-zirconia was completely recoverable up to five successive cycles and there was no noticeable loss in its catalytic activity (Figure 1).

To confirm the heterogeneous nature of the catalyst and to test the stability of surface sulfate ions, a leaching experiment was carried out. The catalyst was retrieved after 1 h. reaction time via filtration by adding ethyl acetate (5 mL), and the further

reaction was continued without any catalyst. There was no increase in yield even after 5 h reaction time, indicating that no leaching of catalyst was involved.

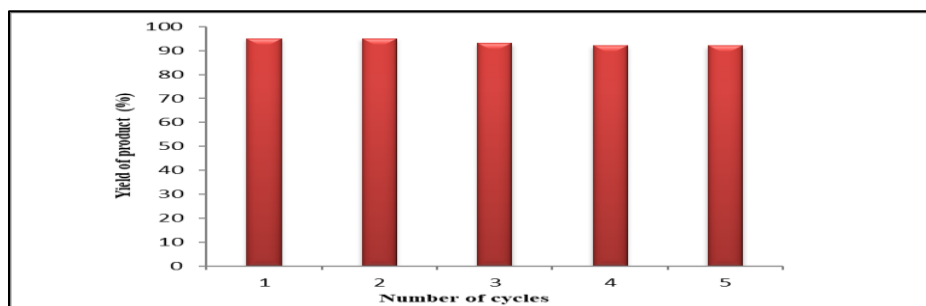




















Fig. 1: Reusability study of SO₄²⁻/Y_{0.16}Zr_{0.84}O₂ for the synthesis of dioxolanes.


IV. CONCLUSIONS

Sulfated yttria-zirconia as surface modified catalysts were successfully intended for the synthesis of 1,3-dioxolanes under solvent free conditions. The catalyst shows remarkable activity tolerance when using structurally varied oxiranes and

carbonyl compounds for the synthesis of acetonides. During the study, it was observed that the catalyst was retrieved simply by filtration with retention of catalytic activity for five sequential cycles.

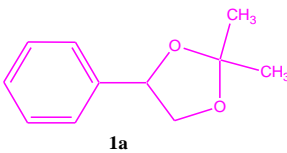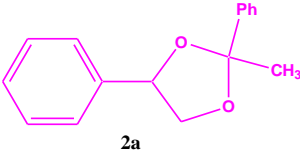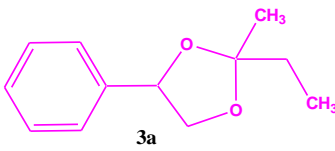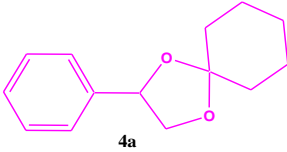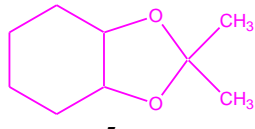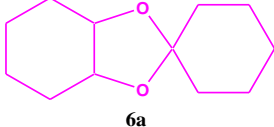Table 2: Sulphated yttria-zirconia catalyzed the synthesis of 1,3-dioxolanes^a

Entry	Epoxide	Ketone	1,3-dioxolane	Yield (%) ^b	Reference
1			 1a	95	[13, 18]
2			 2a	93	[19]
3			 3a	84	[13]
4			 4a	87	[13]
5			 5a	88	[18]
6			 6a	79	[21]

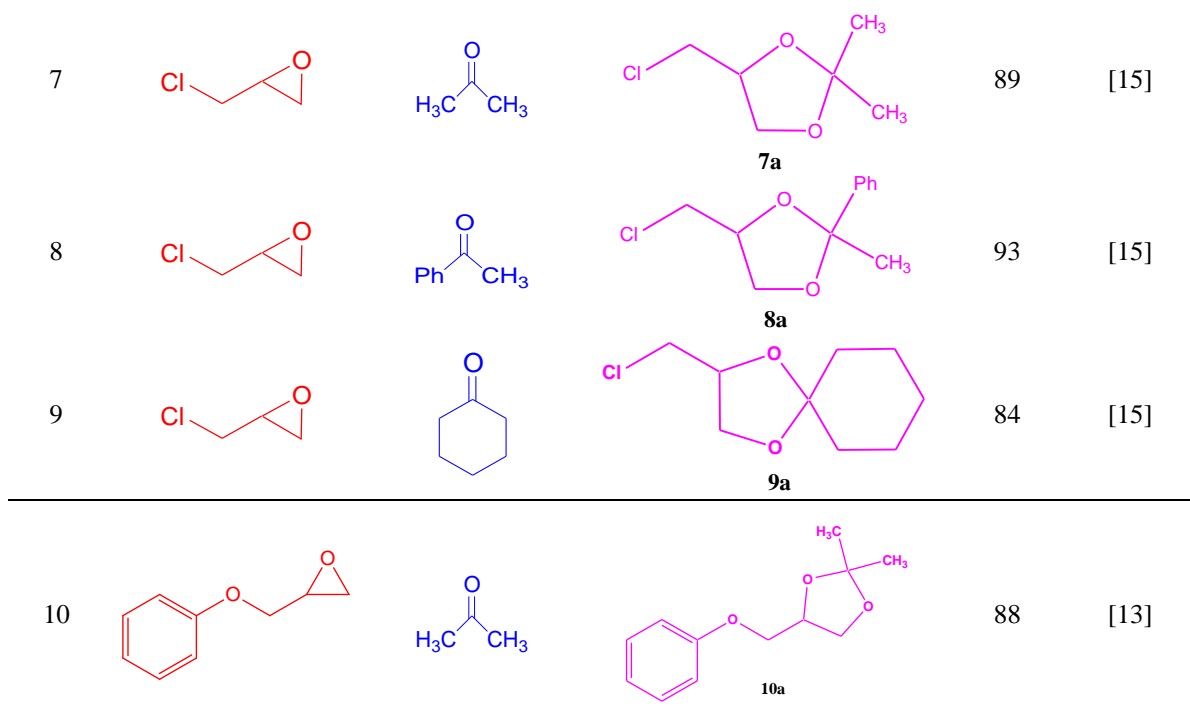

^aReaction conditions: epoxide (3 mmol), ketone (3 mmol), $\text{SO}_4^{2-}/\text{Y}_{0.16}\text{Zr}_{0.84}\text{O}_2$:10 wt% of epoxide, temp. - r.t. (32 °C), time- 2 h, solvent free, ^bIsolated yield.

Among the several catalysts and compositions studied, $\text{SO}_4^{2-}/\text{Y}_{0.16}\text{Zr}_{0.84}\text{O}_2$ was found to be the best in terms of catalytic activity. The simple recovery process of catalyst, mild reaction conditions, recyclability of the catalysts and solvent-free approach makes the procedure preferable to the currently existing methods.

ACKNOWLEDGMENT

The author is thankful to the Vidya Prasarak Mandal and Department of Chemistry, B. N. Bandodkar College of Science, (Autonomous) Thane and Department of Chemistry, Institute of Chemical Technology (ICT), Mumbai for providing Laboratory facilities for work.

REFERENCES

- [1.] BJ Mellor, PE Murray and EJ Thomas, Aspects of the chemistry of dioxolanes: Synthesis of -nucleoside analogues. *Tetrahedron* 1998; 54, 243-256.
- [2.] J Cossy, JL Ranaivosata, B Gille and V Bellosta, Oxidation of substituted spiro[bicyclo[n.1.0] alkane-2,2'-[1,3]dioxolanes] Formation of substituted lactones. *Tetrahedron Lett.* 1999; 40, 4681-4682.
- [3.] K Hirano, T Iwahama, S Sakaguchi and Y Ishi, N-Hydroxyphthalimide-catalyzed radical addition of 1,3-dioxolanes and molecular oxygen to alkenes under ambient conditions: a new route to β -oxycarbonyl compounds. *Chem. Commun.* 2000, 2457-2458.
- [4.] P Camps and X Farres, Stereoselective synthesis of both enantiomers of ketoconazole from (R)- and (S)-epichlorohydrin. *Tetrahedron: Asymmetry* 1995; 6, 1283-1294.
- [5.] M Lee, CK Chu, SB Pai, YL Zhu, YC Cheng, MW Chun and WK Chung, Dioxolane cytosine nucleosides as anti-hepatitis B agents. *Bio. Med. Chem. Lett.* 1995; 5, 2011-2014.
- [6.] MZ Luo, MC Liu, DE Mozdiesz, TS Lin, GE Dutschman, EA Gullen, YC Cheng and AC Sartorelli, Synthesis and biological evaluation of l- and d-configuration 1,3-dioxolane 5-azacytosine and 6-azathymine nucleosides. *Bio. Med. Chem. Lett.* 2000; 10, 2145-2148.
- [7.] JM Bueno, JC Cuevas, JM Fiandor, S Garcia-Ochoa and FG De las Heras, Antifungal sordarins. Synthesis and structure-activity relationships of 3',4'-Fused dioxolane and dioxane derivatives. *Bio. Med. Chem. Lett.* 2002; 12, 121-124.
- [8.] RP Hanzlik and M Leinwetter, Reactions of epoxides and carbonyl compounds catalyzed by anhydrous copper sulfate. *J. Org. Chem.* 1978; 43, 3, 438-440.
- [9.] Bucsi, A. Meleg, A. Molnar and M Bartok, Brønsted acid catalyzed formation of 1,3-dioxolanes from oxiranes and ketones. *J. Mol. Catal. A: Chem.* 2001; 168, 47-52.
- [10.] DS Torok, JJ Figueroa and WJ Scott, 1,3-Dioxolane formation via Lewis acid-catalyzed reaction of ketones with oxiranes. *J. Org. Chem.* 1993; 58, 7274-7276.
- [11.] L W Zatorski and PT Wierchowski, Zeolite-catalyzed synthesis of 4-phenyl-1,3-dioxolanes from styrene oxide, *Catal. Lett.* 1991; 10 (3-4), 211-213.
- [12.] A Gevorgyan, PI Kazarian, OV Anakhyan, A Vardanian and Kim G Soedin, 1991; 33 (Chem. Abstr. 1991, 115, 8633x).
- [13.] M Mirza Aghayan, M Mohammadi, Z Ahmadi and R Boukherroub, Ultrasound Assisted the Synthesis of

- 1,3-Dioxolane Derivatives from the Reaction of Epoxides or 1,2-Diols with Various Ketones Using Graphene Oxide Catalyst. *Catal. Lett.* 2020; 150, 2959–2969.
- [14.] DA Richard, SB Thomas and B Kellie, Synthesis of 1,3-dioxolanes by the addition of ketones to epoxides by using $[\text{Cp}^*\text{Ir}(\text{NCMe})_3]^{2+}$ as catalyst. *J. Organomet. Chem.* 1999; 582, 358–361.
- [15.] AP Amrute, S Sahoo, A Bordoloi, YK Hwang, Jin-Soo Hwang and SB Halligudi, $\text{MoO}_3/\text{SiO}_2$: An efficient and selective catalyst for the synthesis 1,3-dioxolane and 1,3-dioxane. *Catal. Commun.* 2009; 10, 1404–1409.
- [16.] P Krasik, M Bohemier-Bernard and Q. Yu, $\text{Cu}(\text{OTf})_2$ -Catalyzed Selective Opening of Aryl and Vinyl Epoxides with Carbonyl Compounds to Give 1,3-Dioxolanes. *Synlett*, 2005; 5, 854–856.
- [17.] L. Chareonsiriwat and W. Chavasiri, Convenient method for the transformation of epoxide to aldehyde and acetonide mediated by Cr-PLM. *Synth Commun.* 2017; 47, 257–267.
- [18.] B Zeiniazadeh and L Sadighnia, Catalytic Conversion of Epoxides to 1,3-Dioxolanes with Phosphomolybdic Acid (PMA) in Solution and under Solvent-Free Conditions. *Phosphorus, Sulfur, and Silicon.* 2008; 183, 2274–2279.
- [19.] P Trikitiwong, N Sukpirom, S Shimazu and W Chavasiri, Iron oxide-pillared clay catalyzed the synthesis of acetonides from epoxides. *Catal Commun.* 2014; 54, 104–107.
- [20.] A Solladié-Cavallo, E Choucair, M Balaz, P Lupattelli, C Bonini and N Di Blasio, A Mild Stereo- and Enantiospecific Conversion of 2,3-Diaryl-Substituted Oxiranes into 2,2-Dimethyl-1,3-Dioxolanes by an Acetone/Amberlyst 15 System. *Eur. J. Org. Chem.* 2006; 13, 3007–3011.
- [21.] HE Jun-Yi, G Fei-Xue and H Rui-Mao, Heteropolyacid-catalyzed Reaction of Epoxides with Ketones: Efficient Synthesis of 1,3-Dioxolane Derivatives, *Chin. J. Chem.* 2005; 23, 1275-1277.
- [22.] BP Nethravathi, KRK Reddy and KN Mahendra, Synthesis of 2,2-dimethyl-4-phenyl-[1,3]-dioxolane using zeolite encapsulated Co(II), Cu(II) and Zn(II) complexes. *Bull. Chem. Soc. Ethiop.* 2010; 24 (2), 295-298.
- [23.] JR Vyvyan, JA Meyer and KD Meyer, Conversion of Epoxides to 1,3-Dioxolanes Catalyzed by Tin(II) Chloride. *J. Org. Chem.* 2003; 68, 9144-9147.
- [24.] A Keshavaraja, VR Hegde, B Pandey, AV Ramaswamy, P Kumar and T Ravindranathan, An Yttrium-Based Strong Lewis Acid for the Heterogeneous Catalysis of the Diels–Alder Reaction. *Angew. Chem., Int. Ed. Engl.* 1995; 34, 2143–2145.
- [25.] S Ramalingam and P Kumar, Multi-component carbon–carbon bond forming Mannich reaction catalyzed by yttria–zirconia-based Lewis acid. *Catal. Commun.* 2008; 9, 2445–2448.
- [26.] P Kumar, RK Pandey, MS Bodas, SP Dagade, MK Dongare and AV Ramaswamy, Acylation of alcohols, thiols and amines with carboxylic acids catalyzed by yttria–zirconia-based Lewis acid. *J. Mol. Catal. A: Chem.* 2002; 181, 207–213.
- [27.] RK Pandey, SP Dagade, RK Upadhyay, MK Dongare and P Kumar, A facile procedure for tert-butoxycarbonylation of amines promoted by yttria-zirconia based strong Lewis acid catalyst. *ARKIVOC*, 2002; vii, 28–33.
- [28.] RK Pandey, SP Dagade, MK Dongare and P Kumar, Synthesis of Carbamates Using Yttria-Zirconia Based Lewis Acid Catalyst. *Synth. Commun.*, 2003; 33, 4019–4027.
- [29.] SS Kahandal, SR Kale, MB Gawande and RV Jayaram, A mild route for one pot synthesis of 5,6-unsubstituted 1,4-dihydropyridines catalyzed by sulphated mixed metal oxides. *Catal. Sci. Technol.* 2014, 4, 672-680.
- [30.] SS Kahandal, AS Burange, SR Kale, P Prinsen, R Luque and RV Jayaram, An efficient route to 1, 8-dioxo-octahydroxanthenes and-decahydroacridines using a sulfated zirconia catalyst. *Catal. Commun.* 2017; 97, 138-145.
- [31.] SS Kahandal, SR Kale, MB Gawande, R Zboril, RS Varma and RV Jayaram, Greener iodination of arenes using sulphated ceria–zirconia catalysts in polyethylene glycol. *RSC advances*, 2014; 4 (12), 6267-6274.
- [32.] KD Parghi, SR Kale, SS Kahandal, MB Gawande and RV Jayaram, Sequential synthesis of β -amino alcohols using a CeO_2 – ZrO_2 bifunctional catalyst system. *Catal. Sci. Technol.* 2013; 3 (5), 1308-1313.
- [33.] SS Kahandal, SR Kale, ST Disale and RV Jayaram, $\text{SO}_4^{2-}/\text{Ce}_x\text{Zr}_{1-x}\text{O}_2$ -catalyzed Synthesis of *N*-tert-Butylamides from Various Nitriles under Solvent-free Conditions. *Chem. Lett.* 2012; 41 (7), 738-740.
- [34.] SS Kahandal, SR Kale, ST Disale and Radha V. Jayaram, Sulphated yttria–zirconia as a regioselective catalyst system for the alcoholysis of epoxides. *Catal. Sci. Technol.* 2012; 2, 1493–1499.
- [35.] KM Reddy, N Lingaiah, PSS Prasad and I Suryanarayana, Acidity Constants of Supported Salts of Heteropoly Acids Using a Methodology Related to the Potentiometric Mass Titration Technique. *J. Sol.Chem.* 2006; 35, 407-423.